



e-ISSN: 2319-8753 | p-ISSN: 2347-6710

IJRSET

International Journal of Innovative Research in
SCIENCE | ENGINEERING | TECHNOLOGY



INTERNATIONAL JOURNAL OF INNOVATIVE RESEARCH

IN SCIENCE | ENGINEERING | TECHNOLOGY

Volume 12, Issue 5, May 2023

ISSN INTERNATIONAL
STANDARD
SERIAL
NUMBER
INDIA

Impact Factor: 8.423

Effect of Different types of Steel Fibers on Mechanical Performance of Concrete Modified with Fly Ash and Metakaolin

Sourav Sharma¹, Niharika Patel²

P.G. Student, Department of Civil Engineering, GIET University, Gunupur, Odisha, India¹

Assistant Professor, Department of Civil Engineering, GIET University, Gunupur, Odisha, India²

ABSTRACT:The reports of the past investigations have vividly expressed the significance of steel fibers and its contributions in enhancing the performance of concrete. The paper aims at investigating the most efficient and potential steel fiber among all four i.e. hooked, crimped, twisted and straight steel fibers that contributes in boosting the performance and quality of concrete after extensive examinations. Several concrete mixes were examined, incorporated with fly ash (FA) and metakaoline (MK) in various proportions FA35%+MK4.5%,FA40%+MK9%,FA45%+MK13.5%,FA50%+MK18% and each composition is reinforced with four types of steel fibers in varying fractions of 0%, 0.5%, 1% and 1.5% to examine the potential of steel fibers in enhancing the properties of concrete for 28 days and 56 days curing period. After exclusive experimentations, It was finally confirmed that hooked steel fibers composite concrete mixes contributed the best performance among all other types of steel fibers whereas straight steel fibers showed a minimal performance compared to other steel fibers.

KEYWORDS:Compressive strength, flexural strength, steel fibers, fly ash (FA), metakaoline (MK), Hooked Steel Fibers (HSF), Crimped steel fibers (CSF), Twisted steel fibers (TSF), Straight steel fibers (SSF).

I. INTRODUCTION

Concrete forms the most prominent building element in the field of construction industry that has been in use since decades. A lot of efforts have been made to discover the durable and serviceable concrete strong enough to sustain all adverse climatic conditions. Investigations are in progress to develop the sustainable and ecofriendly concrete by modifying with industrial waste materials such as fly ash, silica fume, GGBS etc. that plays a key role in boosting the strength properties of concrete.

Fly ash constitutes the major waste material that is obtained as a residue during the process of incomplete combustion of coal from thermal power stations. Past investigations proved that the replacement of cement with fly ash in concrete greatly improves the strength and durability of concrete.

Metakaoline, nowadays, forms the major pozzolonic material, that is obtained as a byproduct from the calcination process of clay mineral kaoline. It was been in use as a partial substitution of cement in concrete to examine the variations in the behavior of concrete and it was evident from the previous studies that it significantly influences the strength of concrete owing to its fineness property.

Steel fibers are utilized as an additive component in the mix to strengthen the compressive and flexural characteristics of concrete. There are various forms of steel fibers such as hooked steel fibers, crimped, straight, twisted, deformed, intended steel fibers categorized based on its configuration, that has been in use in concrete since decades that highly influenced the properties of concrete. Presently, four types of steel fibers i.e. hooked, crimped, straight and twisted steel fibers are included in every composition of concrete incorporated by fly ash and metakaoline to investigate the impact of steel fibers on the behaviour of concrete which is supported by several past researches discussed briefly.

II. LITERATURE SURVEY

The present work is drafted after referring the following previous researches:

Mahakavi P. et al. (2019), investigated on the effect of inclusion of hooked and crimped steel fibers on the fresh and hardened properties of self-compacting concrete. The results demonstrated that compressive, flexural and impact resistance improved significantly with the combined mix of steel fibers.

Yoo D. et al. (2020), examined the tensile behavior of concrete by introducing corrosion straight steel fibers in various proportions in concrete mix. It was found that corrosion steel fibers enhanced tensile strength by 4 to 6 % without any deterioration of the bond resistance.

Tai Y. et al.(2019), presented the computational model to observe the impact of twisted fiber on the pull out force and frictional behavior. The simulations revealed that maximum pull out force and energy dissipation capacity increased with the decrease in the pitch of the fiber twist.

Yoo D., et at. (2019), experimented on the utilization of different types of steel fibres in ultra-high performance concrete to evaluate the potential of each fiber under extreme loading conditions. Results proved that straight or moderately deformed fibers perform well under extreme loading conditions than hooked and twisted steel fibers.

Larsen I. L. et al. (2020), discussed upon the influence of steel fibers inclusion on compressive and tensile behaviour of ultra-high performance concrete and resulted that steel fibers exhibits major contributions in increase in tensile strength but improvement of compressive strength varies with the geometry of test specimens and other factors.

Hedjazi S., et al.(2020), conducted a comparative analysis on the impact of steel, glass and nylon fibers on the strength and UPV values of concrete. A new empirical approach was proposed to compute the compressive strength of concrete based on the fiber volume fraction.

Holschemacher K., et al. (2010), focused on the variations in the behavior of concrete modified with the utilization of three types of fibers such as straight, hooked and corrugated steel fibers in concrete mix. It was reported that presence of different types of fibers had a major impact on the flexural and tensile performance, fracture behavior and workability of concrete.

Celestine A. et al. (2020), aimed to study the behavior of M30 grade concrete prepared by replacing cement by 8% silica fume with inclusion of crimped steel fibers in varying fractions. Experiments were conducted to investigate the strength of concrete for 7 and 28 days curing.

Shen D., et al. (2019), attempted to research on the contributions of double end hooked steel fibers on the resistance of crack formation of concrete. It was examined that residual and free shrinkage stresses decreased significantly with the inclusion of hooked steel fibers. Wang X., et al. (2019), performed the detailed experimentation to examine the efficiency of the numerous types of steel fibers and its aspect ratio on the strength of steel fiber reinforced cellular concrete. It was confirmed that higher compressive strength greatly depends upon higher steel fiber fractions and aspect ratio.

Liu F. et al. (2019), analyzed the importance of introduction of steel and PVA fibers in concrete to discuss the bending strength and crack resistance of concrete. Results indicated that steel fibers contributed in increasing the bending strength and PVA fibers exhibit better performance in crack resistance.

Han J. et al. (2019), presented the impact of steel fiber length and maximum coarse aggregate size on the strength properties of concrete. After experimentations, it was concluded that ratio of steel fiber to coarse aggregate maximum size had a great impact on fracture toughness, flexural performance and split tensile strength.

Siddique R. et al. (2016), aimed at analyzing the rheological, strength and permeation performance of concrete modified with fly ash and incorporated with steel fibers in varying fractions. It was noticed inclusion of steel fibers greatly enhanced the strength and offered higher resistance to chloride penetration but there was slight increase in porosity.

Guneyis E. et al. (2013), experimented on the concrete mixes with and without inclusion of hooked steel fibers in varying fractions and aspect ratio to evaluate the bond strength. Results clearly indicated that steel fibers play a significant role in enhancing the bond strength and ductility of concrete.

III. MATERIALS USED

1. Cement

Cement is one the major component in the manufacturing process of concrete. It has the property to stick to any other raw material added in the preparation process of concrete, especially when comes in contact with water and hence produces a good paste. Here, OPC 53 grade cement is used whose properties are shown below.

2. Fine Aggregate

Fine aggregate is first graded to decide the zone to which it belongs to. Generally, there are four categories of fine aggregate Zone-I, Zone-II, Zone-III & Zone-IV. In this work, sand of zone-II is chosen whose properties were given below. Generally, fine aggregate is passed through 4.75 mm sieve.

3. Coarse aggregate

Coarse aggregate is another fundamental raw material which gives strength, hardness and increases the volume of the concrete. Here, coarse aggregate of size 20 mm and angular crushed shape is chosen.

4. Fly Ash

Fly ash is widely produced waste material across the globe and it constitutes the major industrial waste throughout, coming out from thermal power stations in the process of combustion of coal. Based on its chemical composition, it is categorized into two types class C and class F. Class C fly ash is highly reactive due to the presence of high content of calcium whereas Class F is slightly inert owing to its less calcium content.

5. Metakaolin

Metakaoline has gained tremendous significance in the construction industry due to pozzolanic characteristics. The calcination process of Kaolinite (China clay) results in the formation of highly pozzolanic reactive raw material Metakaoline. Metakaoline being finer in size and reactive in nature fills up the voids spaces in concrete that improves the mechanical properties of concrete to a huge extent.

6. Steel Fibers

Four types of steel fibers are introduced in our present work which are hooked, crimped, straight and twisted steel fibers which are prepared from the mild steel drawn wires. All fibers are collected from Ajay Enterprises located in Rajgangpur, Odisha and are ensured to maintain the same aspect ratio of 50 with 30 mm length and 0.5 mm diameter, with the tensile strength of 1100 MPa and specific gravity 7.8.

7. Admixture

Superplasticizer "Conplast SP 430" is used for casting of concrete samples. It is made of Sulphonated Naphthalene polymer, specified as per IS: 9103-979 that achieves in reducing the water content by 20%.

8. Water

Normal tap water is utilized in the present work in the preparation of concrete specimens.

IV. EXPERIMENTAL RESULTS & DISCUSSIONS

1. Compressive Strength Results:

Compressive strength results were obtained for all the compositions of concrete mix, modified by fly ash (FA) and metakaoline (MK), incorporated with four types of steel fibers for 28 and 56 days curing duration and are represented clearly in the form of graphs above. A mix of FA25%+MK13.5% with 1% inclusion of hooked steel fibers produced the highest compressive strength of 57.52 MPa for 28 days curing and 67.42 MPa for 56 days curing period, followed by crimped steel fibers, then twisted steel fibers and lastly by straight steel fibers for the same composition. The least compressive strength of 46.62 MPa for 28 days curing and 56.52 MPa for 56 days was exhibited by a mix FA30%+MK18% with 1.5% inclusion of straight steel fibers. Hence, it is evident that FA25%+MK13.5% mix, strengthened with hooked steel fibers performed significantly better compared to other mixes. And hooked steel fibers imparted a huge gain in the compressive performance of all concrete mixes compared to all other steel fibers and straight steel fibers showed the least performance.

28 days compressive strength results.

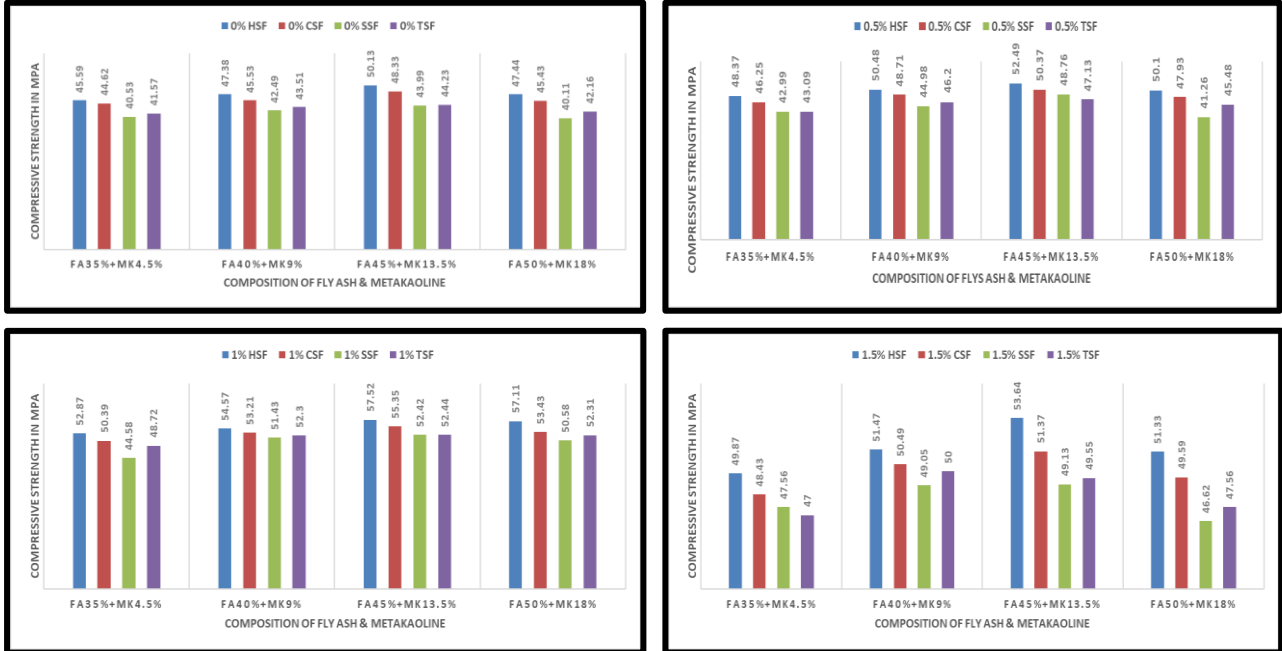


Fig 1. Compressive strength results for FA+MK mixes without any inclusion of steel fibers, **Fig 2.** Compressive strength results for FA+MK mixes reinforced with 0.5% HSF, CSF, SSF & TSF, **Fig 3.** Compressive strength results for FA+MK mixes reinforced with 1% HSF, CSF, SSF & TSF, **Fig 4.** Compressive strength results for FA+MK mixes reinforced with 1.5% HSF, CSF, SSF & TSF

56 days compressive strength results.

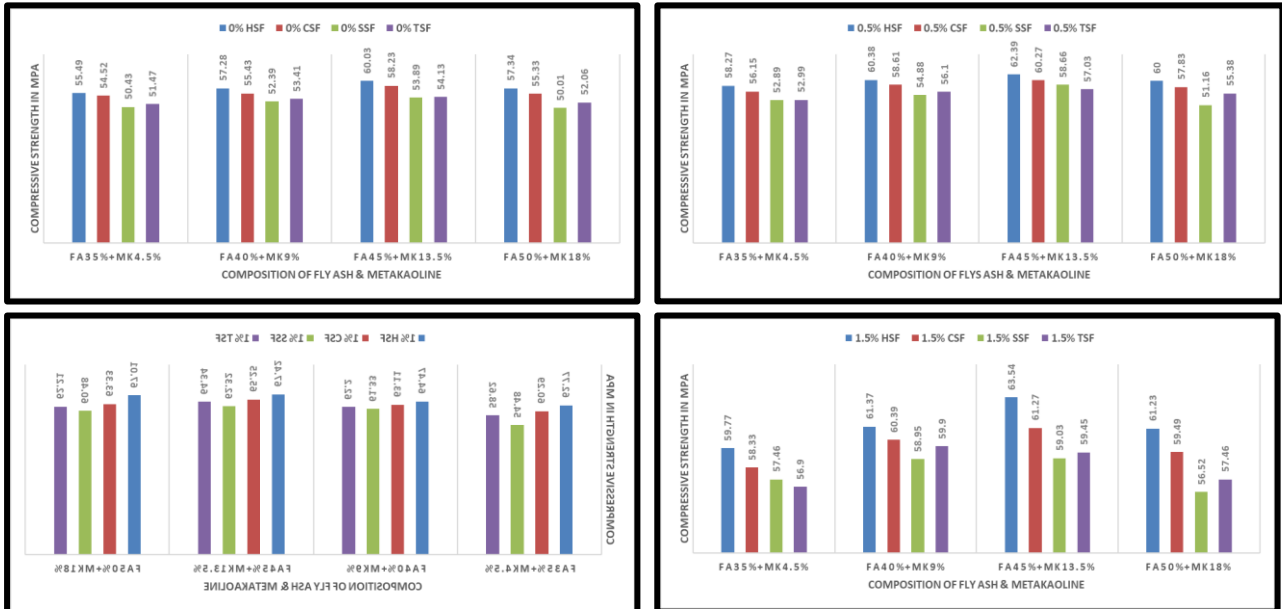


Fig 5. Compressive strength results for FA+MK mixes without any inclusion of steel fibers, **Fig 6.** Compressive strength results for FA+MK mixes reinforced with 0.5% HSF, CSF, SSF & TSF, **Fig 7.** Compressive strength results for FA+MK mixes reinforced with 1% HSF, CSF, SSF & TSF, **Fig 8.** Compressive strength results for FA+MK mixes reinforced with 1.5% HSF, CSF, SSF & TSF

2. Flexural Strength Results:

Flexural strength results were evaluated for all the compositions of concrete mix, modified by fly ash (FA) and metakaoline (MK), incorporated with four variants of steel fibers for 28 and 56 days curing duration and are represented clearly in the form of graphs above. A mix of FA25%+MK13.5% with 1% reinforcement of hooked steel fibers produced the maximum flexural strength of 7.34 MPa for 28 days curing and 8.25 MPa for 56 days curing period, followed by crimped steel fibers, then twisted steel fibers and lastly by straight steel fibers for the same composition. The least flexural strength of 5.44 MPa for 28 days curing and 6.34 MPa for 56 days was exhibited by a mix FA30%+MK18% with 0% inclusion of straight steel fibers. Therefore, it is evident that FA25%+MK13.5% mix, strengthened with hooked steel fibers performed significantly better compared to other mixes overall. And hooked steel fibers imparted a huge gain in the flexural performance of all concrete mixes compared to all other steel fibers and straight steel fibers showed the least performance.

28 days Flexural strength results.

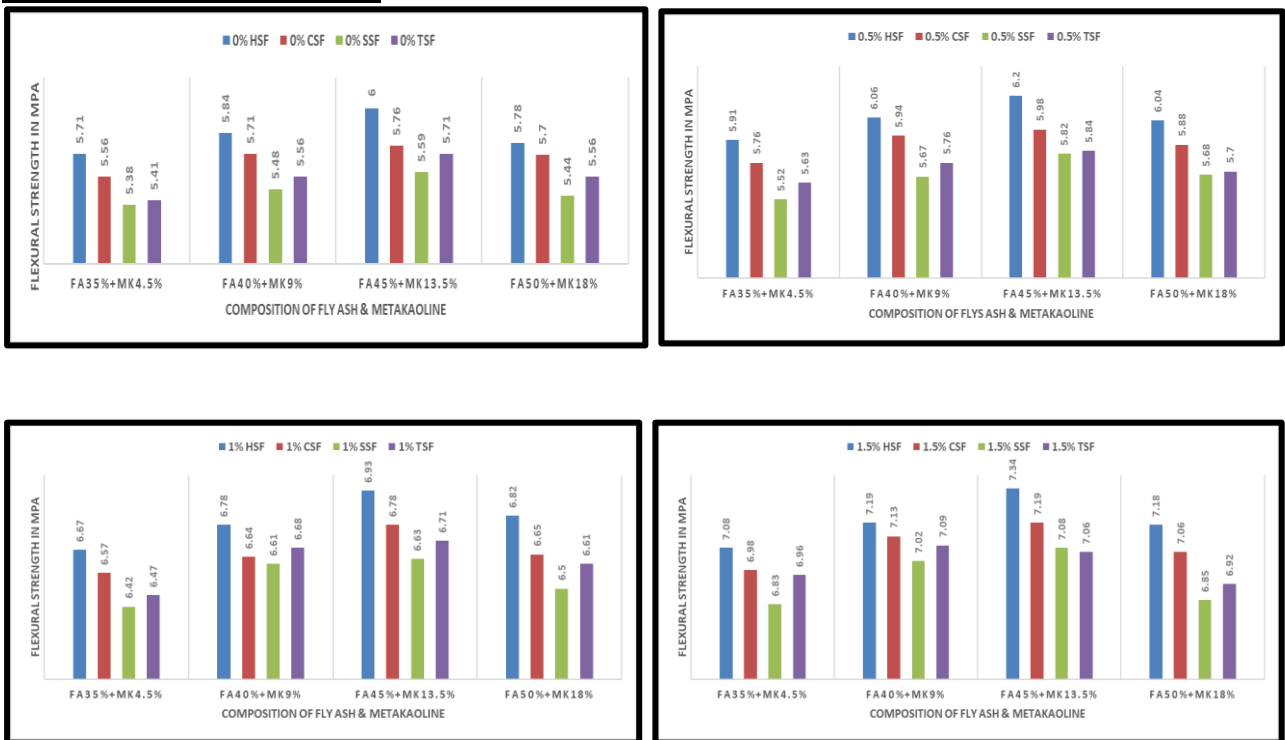


Fig 9. Flexural strength results for FA+MK mixes without any inclusion of steel fibers, **Fig 10.** Flexural strength results for FA+MK mixes reinforced with 0.5% HSF, CSF, SSF & TSF, **Fig 11.** Flexural strength results for FA+MK mixes reinforced with 1% HSF, CSF, SSF & TSF, **Fig 12.** Flexural strength results for FA+MK mixes reinforced with 1.5% HSF, CSF, SSF & TSF

56 days Flexural strength results.

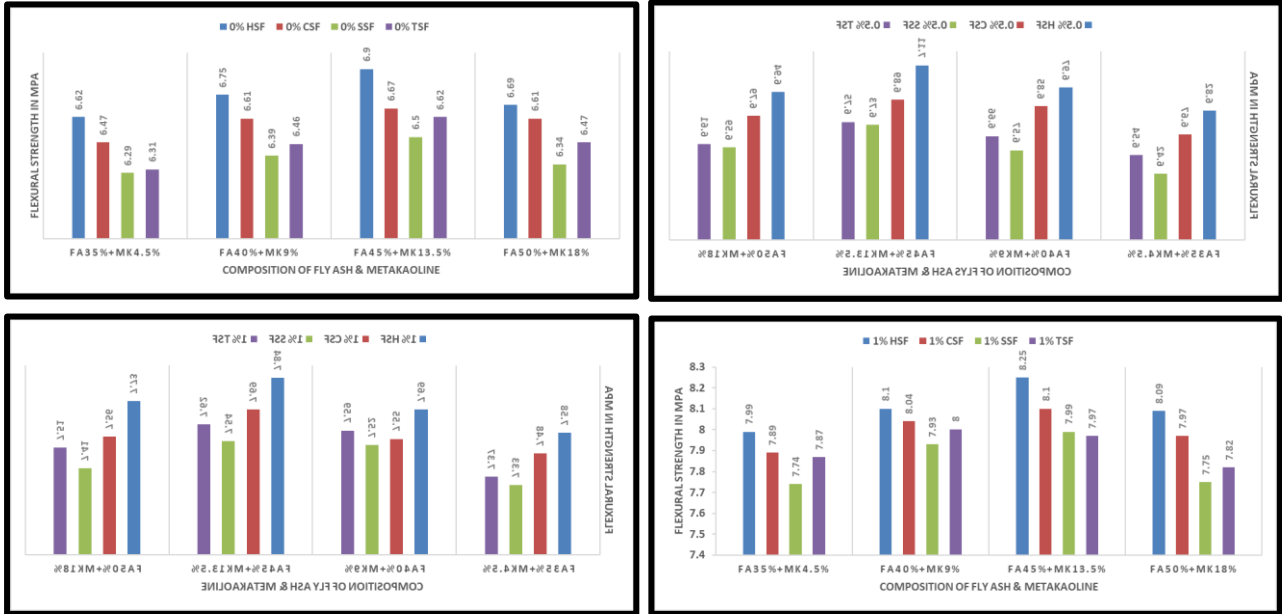


Fig 13. Flexural strength results for FA+MK mixes without any inclusion of steel fibers, **Fig 14.** Flexural strength results for FA+MK mixes reinforced with 0.5% HSF, CSF, SSF & TSF, **Fig 15.** Flexural strength results for FA+MK mixes reinforced with 1% HSF, CSF, SSF & TSF, **Fig 16.** Flexural strength results for FA+MK mixes reinforced with 1.5% HSF, CSF, SSF & TSF

3. Porosity Results:

It is observed that all concrete mix compositions, incorporated with hooked steel fibers performed significantly well in bridging the voids and a mix of FA45%+MK13.5% with 0% inclusion of HSF exhibited lowest porosity value of 6.48% among all compositions. Comparatively, all concrete mix substitutions, included with straight steel fibers contributed highest porosity values, compared to other steel fibers and a mix of FA35%+MK4.5% with 1.5% SSF showed the peak porosity of 8.46%. It is examined that porosity increased with rise in percentage addition of steel fibers of all types for all concrete mixes modified with FA and MK.

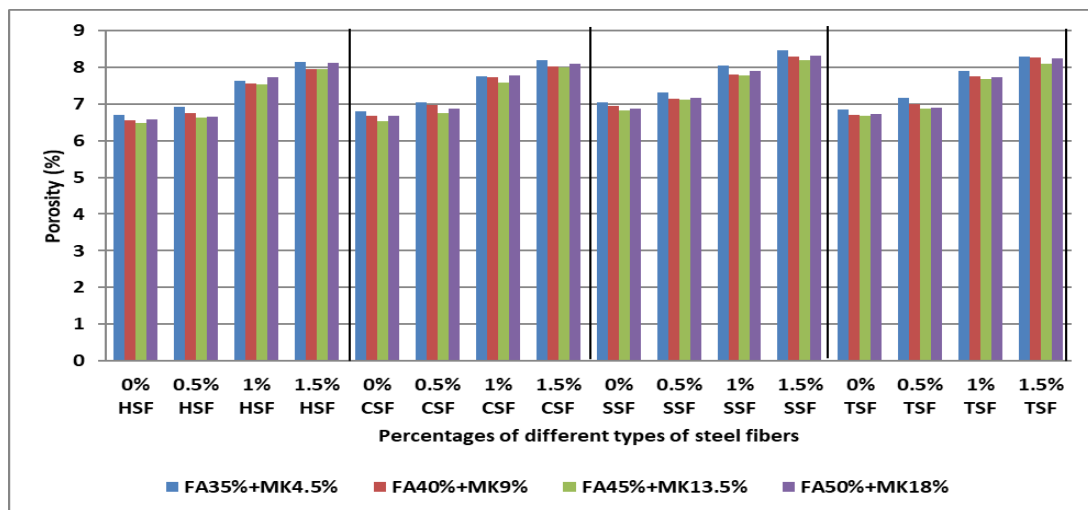


Fig 17. Cumulative graph showing the variations in porosity results for all concrete compositions included with different fractions of HSF, CSF, SSF & TSF

4. Ultra Sonic Pulse Velocity Results:

It is observed that all concrete mix compositions, incorporated with hooked steel fibers showed better performance and a mix of FA45%+MK13.5% with 0% inclusion of HSF exhibited value of 4.8 km/s among all compositions which denotes less presence and formations of voids in these mixes. Subsequently, all concrete mix substitutions, included with straight steel fibers exhibited least values of UPV values, compared to other steel fibers that depicts the presence of more voids in the mixes and a mix of FA35%+MK4.5% with 1.5% SSF showed the least value of 3.44 km/s. It is noticed that ultrasonic pulse velocity values declined with the increase in percentage inclusion of all types of steel fibers for all mix substitutions. However, all the mix compositions fall under the category of excellent and good quality as per ASTM C597.

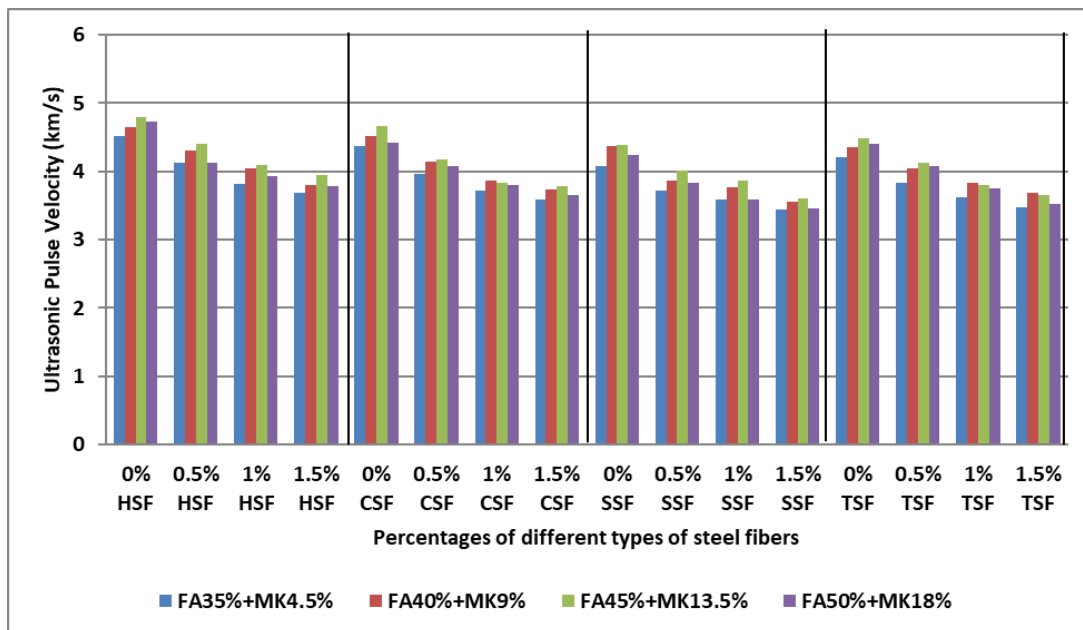


Fig 18. Cumulative graph showing the variations in UPV results for all concrete compositions included with different fractions of HSF, CSF, SSF & TSF

V. CONCLUSIONS

Following conclusions were extracted from the results and discussions obtained:

- 1) All compositions with hooked steel fibers showed extremely good compressive performance, followed by crimped, twisted and straight steel fibers respectively.
- 2) Highest compressive strength of 57.52 N/mm² is achieved by a composition of FA45%+MK13.5% with 1% hooked steel fibers among all other compositions for 28 days curing.
- 3) Highest compressive strength of 67.42 N/mm² is achieved by a composition of FA45%+MK13.5% with 1% hooked steel fibers among all other compositions for 56 days curing.
- 4) Excellent flexural performance was exhibited by all concrete mixes reinforced with hooked steel fibers, followed by crimped, twisted and straight steel fibers respectively.
- 5) A mix of FA45%+MK13.5% included with 1.5% hooked steel fibers yielded maximum flexural strength of 7.34 N/mm² and 7.99 N/mm² for 28 and 56 days curing respectively among all other mixes.
- 6) Concrete mixes hybridized by FA+MK, especially strengthened by hooked steel fibers exhibited least porosity values, followed by crimped, twisted and straight steel fibers respectively.
- 7) Concrete mix hybridized by FA45%+MK13.5% with 0% hooked steel fibers yielded the least porosity value of 6.48% among all mix proportions.
- 8) All concrete mixes incorporated with hooked steel fibers falls under the category of excellent quality determined as per ultrasonic pulse velocity test. This signifies that all these mixes are having fewer voids than other mixes.
- 9) A combined replacement level of FA45%+MK13.5% performed significantly better compared to other combinations of FA and MK.

- 10) Inclusion of hooked steel fibers in concrete compositions contributed excellent overall performance and proved to be the most efficient fiber among all fibers
- 11) Straight steel fibers exhibited least performance in terms of compressive, flexural, porosity and quality among all other fibers.

REFERENCES

- [1] Mahakavi P., Chithra R., (2019), Impact resistance, microstructures and digital image processing on self-compacting concrete with hooked end and crimped steel fiber. *Construction and Building Materials*, Vol. 220, pp: 651-666, <https://doi.org/10.1016/j.conbuildmat.2019.06.001>
- [2] Yoo D., Shin W., chun B., (2020), Corrosion effect on tensile behavior of ultra- high- performance concrete reinforced with straight steel fibers. *Cement and Concrete Composites*, Vol. 109, <https://doi.org/10.1016/j.cemconcomp.2020.103566>
- [3] Tai Y., Tawil S., (2019), Computational investigation of twisted fiberpullout from ultra-high performance concrete. *Construction and Building Materials*, Vol. 222, pp: 229-242, <https://doi.org/10.1016/j.conbuildmat.2019.06.146>
- [4] Yoo D., Kim J., Chun B., (2019), Dynamic pulloutbehavior of half-hooked and twisted steel fibers in ultra-high-performance concrete containing expansive agents. *Composites Part B: Engineering*, Vol. 167, pp: 517-532, <https://doi.org/10.1016/j.compositesb.2019.03.022>
- [5] Larsen I. L., Thorstensen R. T., (2020), The influence of steel fibers on compressive and tensile strength of ultra-high performance concrete: A review. *Construction and Building Materials*, Vol. 256, <https://doi.org/10.1016/j.conbuildmat.2020.119459>
- [6] Hedjazi S., Castillo D., (2020), Relationships among compressive strength and UPV of concrete reinforced with different types of fibers. *Heliyon*, Vol. 6, Issue 3 , <https://doi.org/10.1016/j.heliyon.2020.e03646>
- [7] Holschemacher K., Mueller T., Ribakov Y., (2010), Effect of steel fibers on mechanical properties of high strength concrete. *Materials & Design (1980-2015)*, Vol. 31, pp: 2604-2615, <https://doi.org/10.1016/j.matdes.2009.11.025>
- [8] Celestine A., Prakash M., Satyanarayanan K.S., Surya T.R., Parthasarathi N., (2020), The interpretation of mechanical study of concrete using crimped steel fibers. *Materials Today: Proceedings*, <https://doi.org/10.1016/j.matpr.2020.04.065>
- [9] Shen D., Kang J., Yi X., Zhou L., Shi X., (2019), Effect of double hooked end steel fiber on early age cracking potential of high strength concrete in restrained ring specimens. *Construction and Building Materials*, Vol. 223, pp: 1095-1105, <https://doi.org/10.1016/j.conbuildmat.2019.07.319>
- [10] Wang X., Zhang S., Wang C., Cao K., Wei P., Wang J., (2019), Effect of steel fibers on the compressive and splitting tensile behaviors of cellular concrete with millimeter size pores. *Construction and Building Materials*, Vol. 221, pp: 60-73, <https://doi.org/10.1016/j.conbuildmat.2019.06.069>
- [11] Liu F., Ding W., Qiao Y., (2019), Experimental investigation on the flexural behavior of hybrid steel-PVA fiber reinforced concrete containing fly ash and slag powder. *Construction and Building Materials*, Vol. 228, <https://doi.org/10.1016/j.conbuildmat.2019.116706>
- [12] Han J., Zhao M., Chen J., Lan X., (2019), Effects of steel fiber length and coarse aggregate maximum size on mechanical properties of steel fiber reinforced concrete. *Construction and Building Materials*, Vol. 209, pp: 577-591, <https://doi.org/10.1016/j.conbuildmat.2019.03.086>
- [13] Siddique R., Kaur G., Kunal, (2016), Strength and permeation properties of self-compaction concrete containing fly ash and hooked steel fibers. *Construction and Building Materials*, Vol. 103, pp: 15-22, <https://doi.org/10.1016/j.conbuildmat.2015.11.044>
- [14] Guneyisi E., Gesoglu M., Ipek S., (2013), Effect of steel fiber addition and aspect ratio on bond strength of cold bonded fly ash light weight aggregate concretes. *Construction and Building Materials*, Vol. 47, pp: 358-365, <https://doi.org/10.1016/j.conbuildmat.2013.05.059>
- [15] Gesoglu M., Guneyisi E., Alzebaree R., Mermerdas K., (2013), Effect of silica fume and steel fiber on the mechanical properties of the concretes produced with cold bonded fly ash aggregates. *Construction and Building Materials*, Vol. 40, pp: 982-990, <https://doi.org/10.1016/j.conbuildmat.2012.11.074>
- [16] Koksai F., Altun F., Yigit I., Sahin Y., (2008), Combined effect of silica fume and steel fiber on the mechanical properties of high strength concretes. *Construction and Building Materials*, Vol. 22, pp: 1874-1880, <https://doi.org/10.1016/j.conbuildmat.2007.04.017>



- [17] Mastali M., Dalvand A., (2016), Use of silica fume and recycled steel fibers in self-compacting concrete. *Construction and Building Materials*, Vol. 125, pp: 196-209, <https://doi.org/10.1016/j.conbuildmat.2016.08.046>
- [18] Afroughsabet V., Biolzi L., Monteiro P.J.M., (2018), The effect of steel and polypropylene fibers on the chloride diffusivity and drying shrinkage of high strength concrete. *Composites Part B: Engineering*, Vol. 139, pp: 84-96, <https://doi.org/10.1016/j.compositesb.2017.11.047>
- [19] Xie J., Zhang Z., Lu Z., Sun M., (2018), Coupling effect of silica fume and steel fiber on the compressive behavior of recycled aggregate concrete after exposure to elevated temperature. *Construction and Building Materials*, Vol. 184, pp: 752-764, <https://doi.org/10.1016/j.conbuildmat.2018.07.035>
- [20] Shukla A., Gupta N., Kishore K., (2020), Experimental investigation on the effect of steel fiber embedded in marble dust based concrete. *Materials Today: Proceedings*, <https://doi.org/10.1016/j.matpr.2020.02.607>
- [21] Ameri F., Brito J. D., Madhkhan M., Taheri R.A., (2020), Steel fiber reinforced high strength concrete incorporating copper slag: Mechanical, gamma ray shielding, impact resistance and microstructural characteristics. *Journal of Building Engineering*, Vol. 29, <https://doi.org/10.1016/j.jobe.2019.101118>



SJIF Scientific Journal Impact Factor

Impact Factor: 8.423



INTERNATIONAL JOURNAL OF INNOVATIVE RESEARCH

IN SCIENCE | ENGINEERING | TECHNOLOGY

 9940 572 462  6381 907 438  ijirset@gmail.com



www.ijirset.com

Scan to save the contact details